

# Particle Identification

Markus Lankers, PhD  
November 2022




## Root cause, particle characterization

*Investigation ..... regarding the metal particulate contamination in lots ..... was inadequate ..... The atypical contamination found in these lots was metal, however, the batches were not rejected. Additionally, there was **no investigation** conducted to determine the cause of the black metal particulates found in these lots*


*“reported a particle identified in a vial during an AQL inspection. **There was no documentation on the identity of the particle and whether it was inherent or foreign (black debris, fiber, glass fragments, etc.).**”*

2015

- Use the Trending Data from Reject Characterization and Monitoring
- Review the various particulate sources for Process Improvement opportunities
- Focus on the most predominant particle types
- Repeat the Cycle of Monitoring, Trending, Corrective actions and follow-up Monitoring

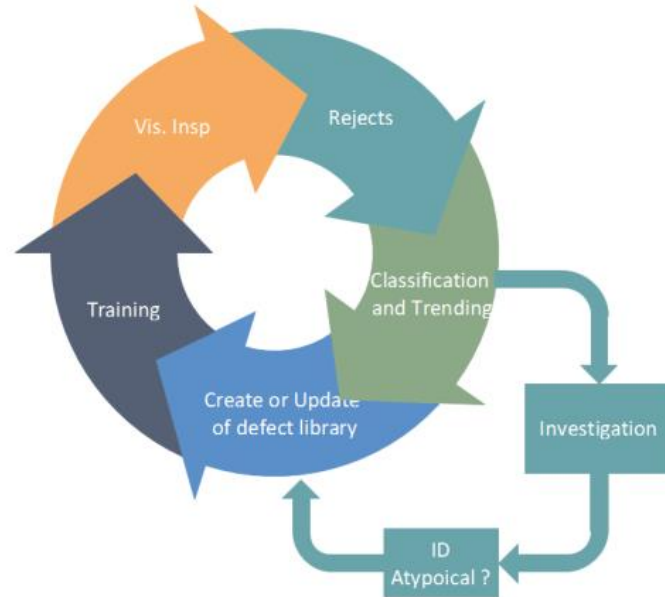

# Classification and Trending

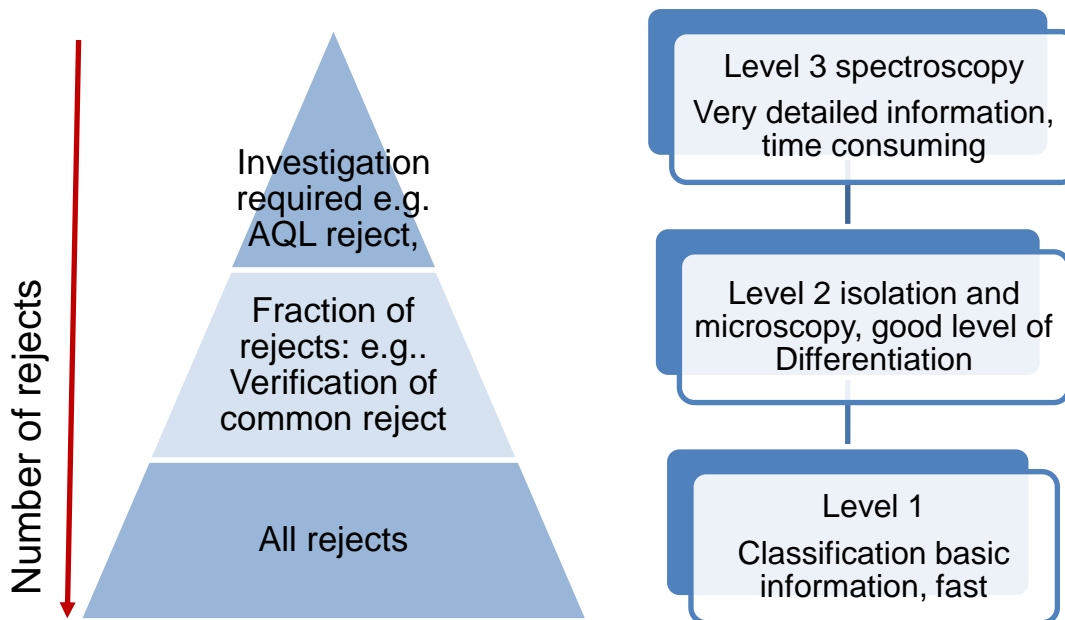

Level One: Visual classification (in-Situ)

- Nondestructive, as seen during manual inspection
- Light, dark, sinking, floating, color, shape, etc.



Level Two: Macroscopic and Microscopic

- Rapid characterization to specific material categories
- Metallic, glass, rubber, plastic, fiber (natural or synthetic), silicone lubricant, inherent particles, etc.



Level Three: Spectroscopic or other fingerprint ID

- FTIR, Raman, Elemental, Mass Spec, etc.

Roy Cherris Visual Inspection Forum 2013, Bethesda

Level		Cost	time/particle
1	light microscopy	Invest: 2T€ €	15 min
2	Isolation, Polarized Light microscopy	Invest: 60 T€	30 min
3	SEM / Raman/ IR	Invest: 70 T€ (IR), 150 T€ (Raman), 180 T€ (SEM)	30 min

1. Classification is based on basic observations  
Defined by trajectory, shape, density
2. Classification could be done by a  
experienced operator probably trained for  
special tools
3. Reason to go on with level 2 characterization  
could be statistics, uncertainty about nature  
of the particle





## Categories

Category		Category	
<b>Glass-Like</b>	[ ]	Polymeric-like	[ ]
<b>Metallic-like</b>	[ ]	Dark Particle	[ ]
<b>Fiber-like</b>	[ ]	Light Particle	[ ]

## Attributes for further description

Shape	Colour	Location	Density	Size
Spherical	Light	Body	Floaters	
Irregular	Dark	Bottom	Fixed	
Elongated	Transparent	Shoulder		

Level 1 characterization groups e.g. dark particle, light particles, fiber-like might be sampled by a basic universal sampling plan like  $\sqrt{N+1}$

Isolation is required for further investigation

Clean area mandatory:

- clean room, clean bench, ultra cleaned glassware, requires trained personnel

Various tools for isolation:

- Capillary, tungsten needles, filtration

Microscope helps to give further details:


- Rubber, metal, synthetic vs natural fiber, crystal shape, color








After isolation particle can be easily transferred to level three

Incident Light	Select	Transmitted Light	Select	Level II Category	Select	Level II Category	Select
Clear	[ ]	Transparent	[ ]	<b>Glass</b>	[ ]	<b>Polymeric</b>	[ ]
Opaque	[ ]	Opaque	[ ]	<b>Metallic</b>	[ ]	<b>Rubber Stopper</b>	[ ]
Reflective	[ ]	Crystalline	[ ]	<b>Fiber</b>	[ ]	<b>Semi-Solid - Silicone</b>	[ ]
<b>Physical</b>	<b>Select</b>	<b>Crossed Polars</b>	<b>Select</b>	<b>Fiber - Natural</b>	[ ]	<b>Possible Inherent API</b>	[ ]
Crystalline	[ ]	Isotropic	[ ]	<b>Fiber - Synthetic</b>	[ ]	<b>Possible Extrinsic</b>	[ ]
Shaving	[ ]	Anisotropic	[ ]				
Resilient	[ ]	Pseudo-Birefringence	[ ]				
Shard	[ ]	Isotropic Rod	[ ]				
Size Length (um)		Uniform fiber	[ ]				
Size Width (um)		Irregular frayed fiber	[ ]				

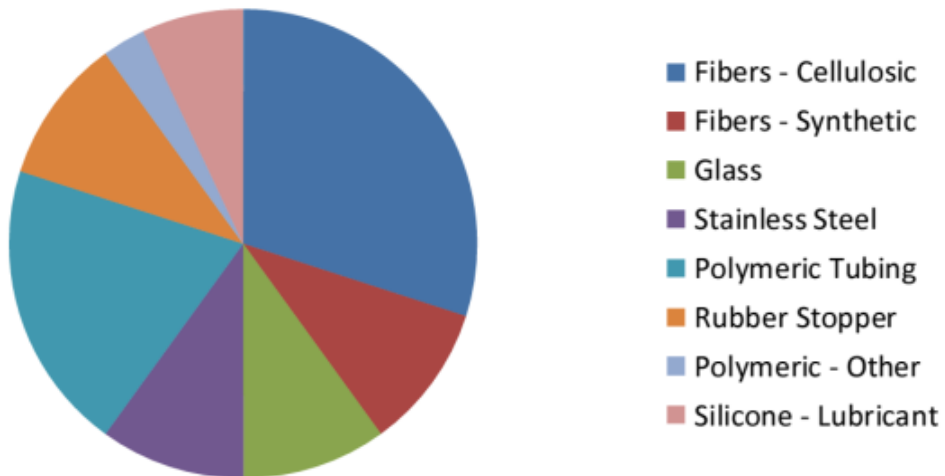


**Level Two Visible Particle ID Trending**



method	meaning		time/particle
PLM (polarized light microscopy)	color + shape e.g.: black fibres		1-5 min
SEM/EDS analysis	> 5µm Elements	 	20-180 min
IR – microscopy	> 50 µm Structure	 	20-180 min
RAMAN - microscopy	> 0.5 µm Structure	 	20-180 min

Category	Select
Glass-Like	[ ]
Metallic-like	[ ]
Fiber-like	[ x ]

Category	Select
Polymeric-like	[ ]
Dark Particle	[ ]
Light Particle	[ x ]

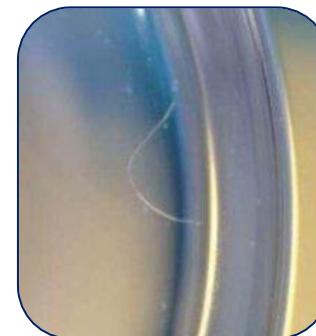

- Fibers can be easily classified. Might be sufficient for trending
- Further classification of fibers can be preformed in situ with an inverted microscope due to morphology and texture

- Microscopy of isolated fiber gives further information (cotton, protein based fiber, synthetic)
- Spectroscopy can give a very specific fingerprint for root cause or kind if synthetic fiber



Level 2



Level 2



Level 1

- Characterized density and reflectivity
- Sufficient for trending
- Hard to observe while swirling
- Usually easy to find at the bottom



Level 1




Level 2




Level 2




Spectroscopy gives more detailed information on the kind of steel e.g. low alloyed vs high alloyed steel which might be needed for root cause investigation

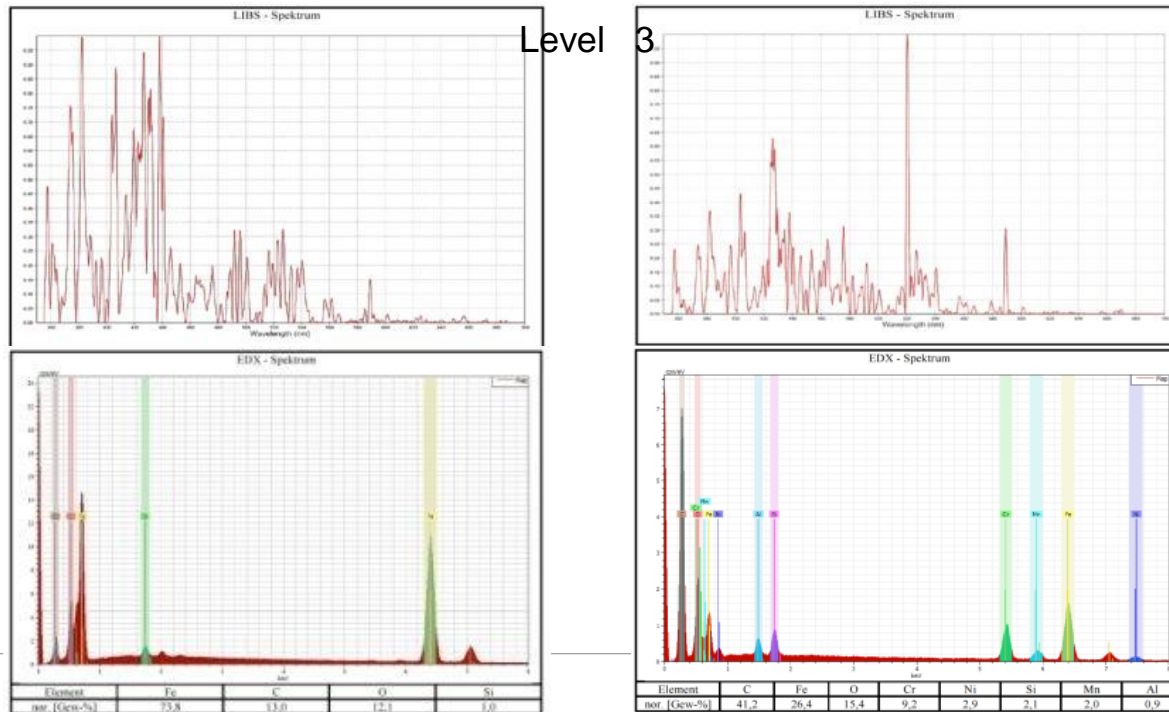

- Glass has a very characteristic shape which is sufficient for classification
- Further characterization for root cause investigation: element specific methods e.g. SEM or LIBS favorable

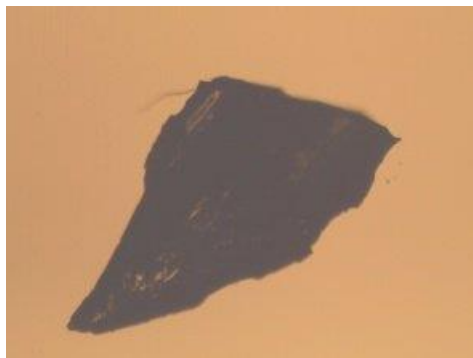


Level 1

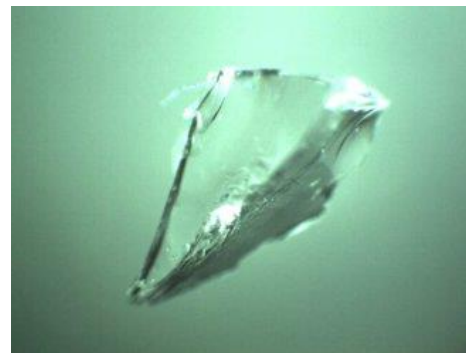


Level 2

# Glass particle Level 3

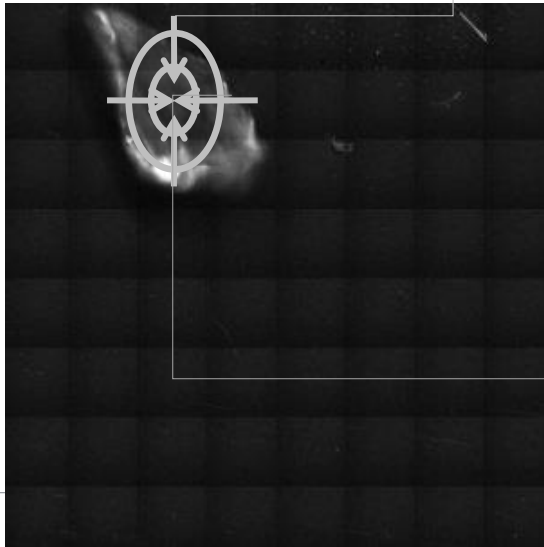


LIBS

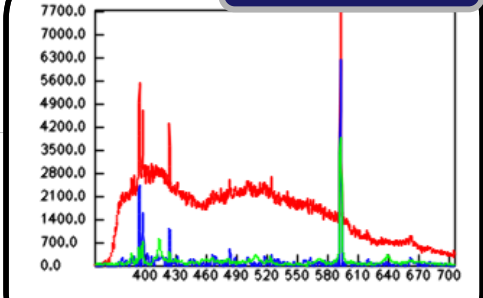

Si, Na, Al (Fiolax)

Raman

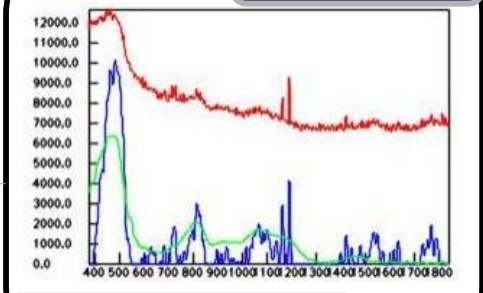

Glass

# Particle Isolation



## Isolation


- Class 100 clean bench is essential
- „Ball-park“ clean rooms would be beneficial
- Cleaning is essential and system suitability tests (blanks) have to be taken
- Training and control is essential
- Benches, coats, sleeves, microscopes, equipment and water should be clean and non-shedding




Tungsten needles for particle picking



Capillary trapping

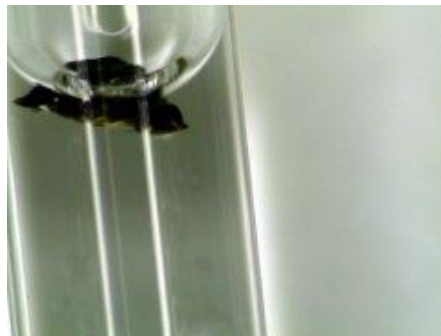

Sending particles to a lab between 2 slides

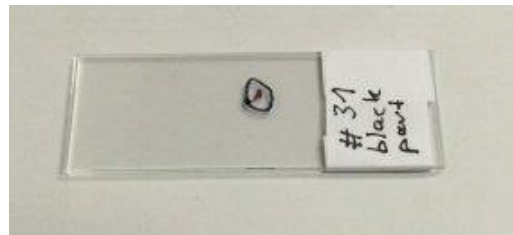

# Particle Sources



## **Inherent**

Particulate made entirely of components of the formulated product, arising from the product itself. These particulates are related to the product formulation: API

## **Intrinsic**

Particulate related to the production process of components of the formulated product, arising from the product itself. Processing Equipment, Primary Package, Active and other ingredients

## **Extrinsic (Foreign)**

Environmental Contaminants  
insect parts, hair, fibers, paint, rust


- personnel




- Garnement
- Water
- container



- Process /  
Production  
Equipment e.g.:  
rubber
- Cleaning process

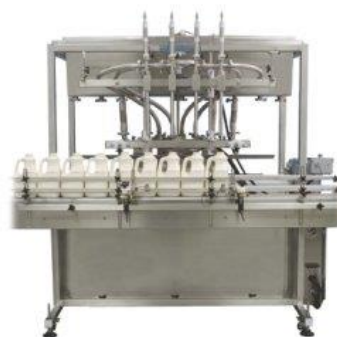


# Visible

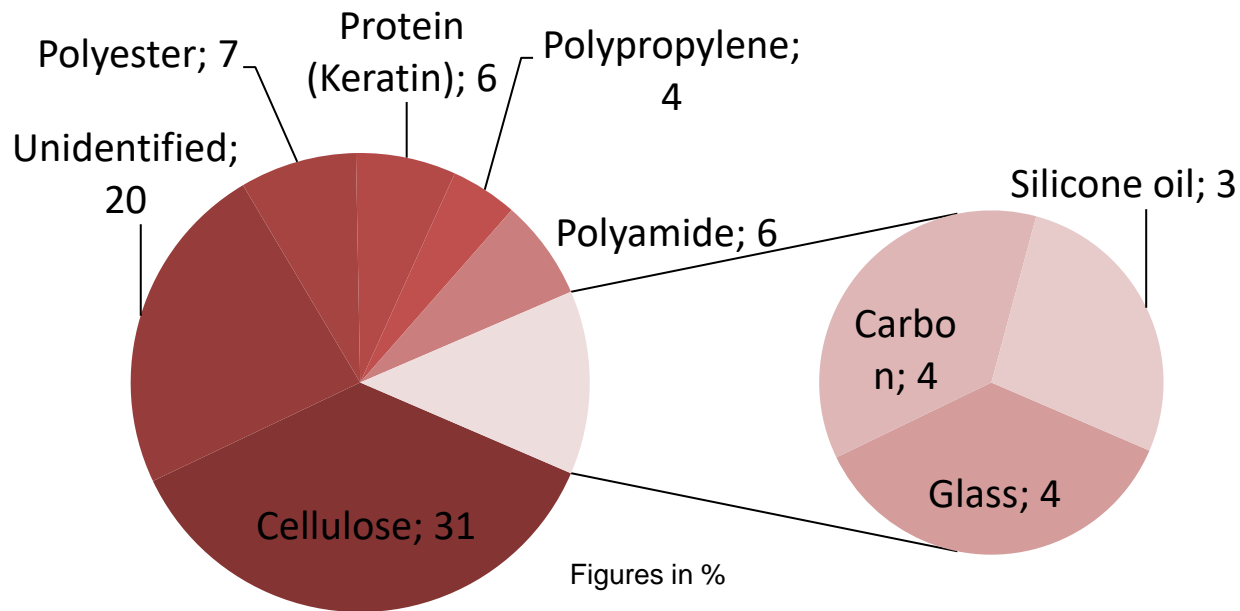

Cellulose, Polyester and Protein/Polyamide particles

# Sub-visible

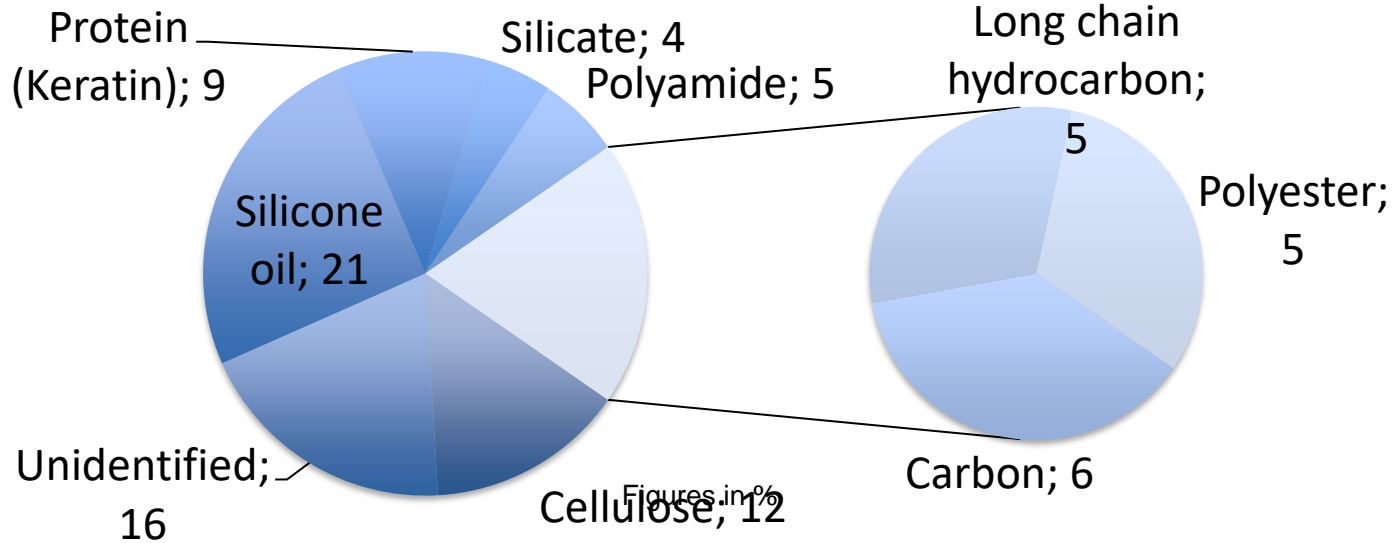

Silicone oil, Protein, Cellulose particles are the most often found contaminants

- Cellulose: mostly fibres
  - source: clothes, **towels**, wipers, autoclave paper




- Longchain hydrocarbon
  - source: rubber (stopper), PE (bottles)


- Glass: fibres and particles
  - Source: Primary packaging
  - But also glassfibers and hollow glass fibres (filter material)
- Carbon: particles
  - Usually black particles contain high content of carbon:
  - Sealings rubber material filled with carbon
  - Burned material




- Polyester: fibres and particles
  - Source: Cleanroom clothes and defect filter
- Protein: mostly flakes
  - Source human dust, protein particles from protein solution
- Silicone oil: compact particles
  - Source: sealings, siliconisation



- White or black spots on/between lips
- Foreign material trapped between plunger and glass wall Glass bits
- Rubber chunks
- Fibres
- Hair

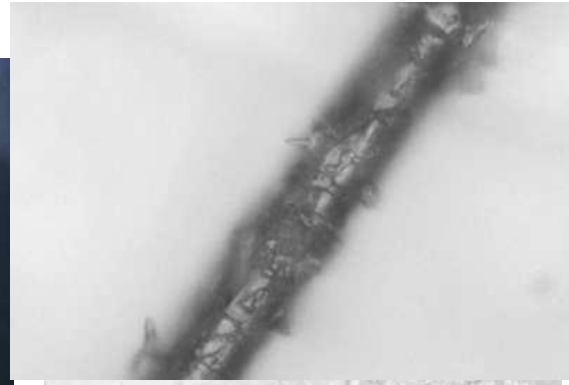




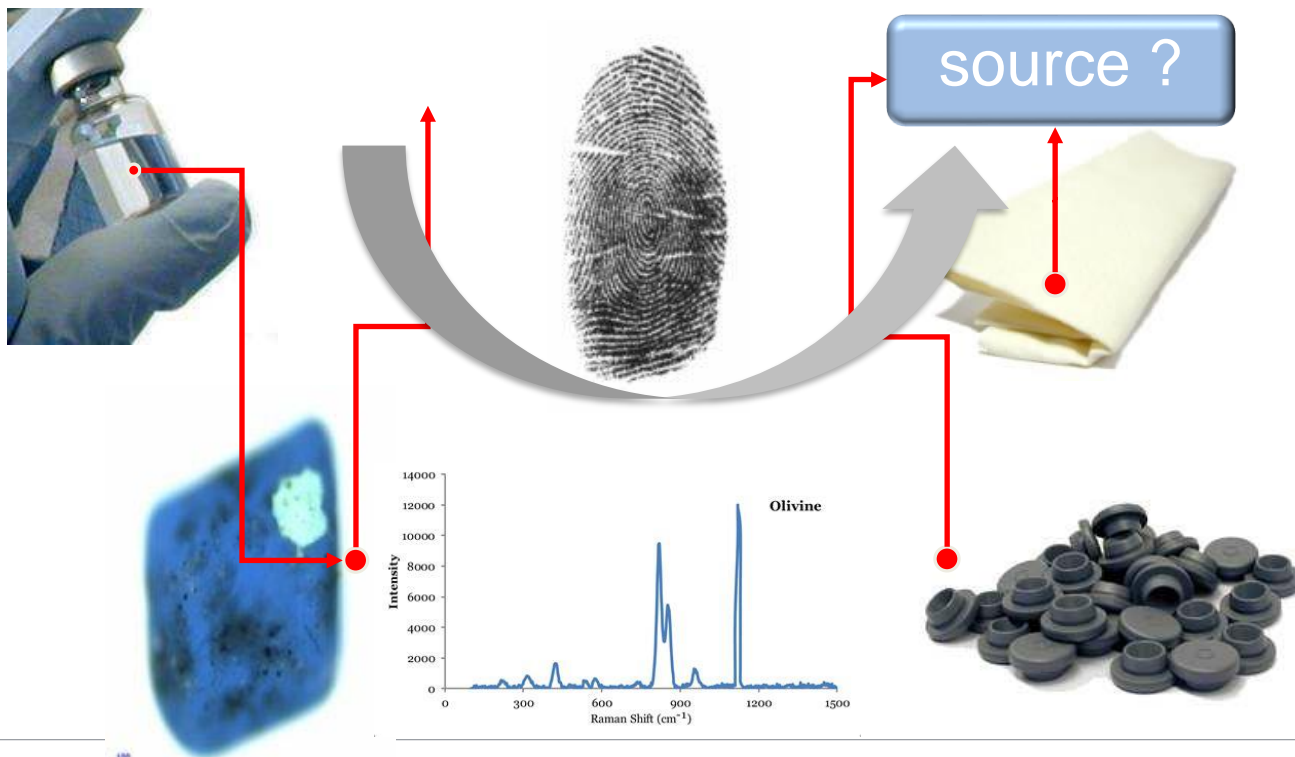





1. Documentation of the defect → in-situ (in the closed container)
2. Filtration and documentation of the sample on the membrane filter
3. Documentation of the analysis and the identification of the reject by Raman spectroscopy
4. Identification of sub-visible to gather further information
5. Verification of the findings (particle observed by visible inspection) with FT-IR or LIBS, EDX

# Particle in a vial



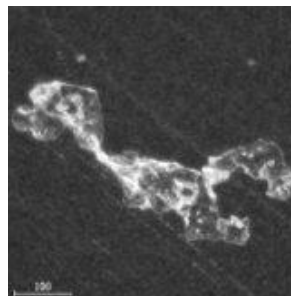
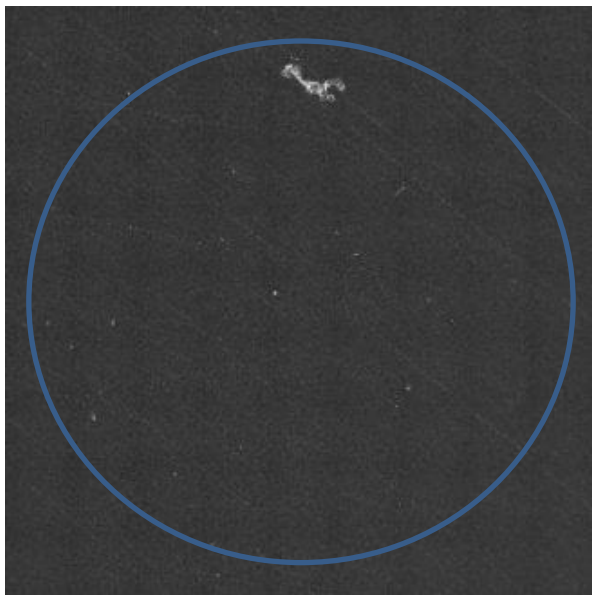



L=505.0  $\mu\text{m}$   
w=202.6  $\mu\text{m}$   
E=2.49  
R=0.3071

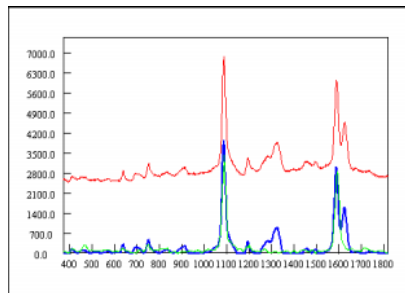



Raman.ID: Polyethylene-terephthalate, PET  
Rank: 887

# Verification by FTIR

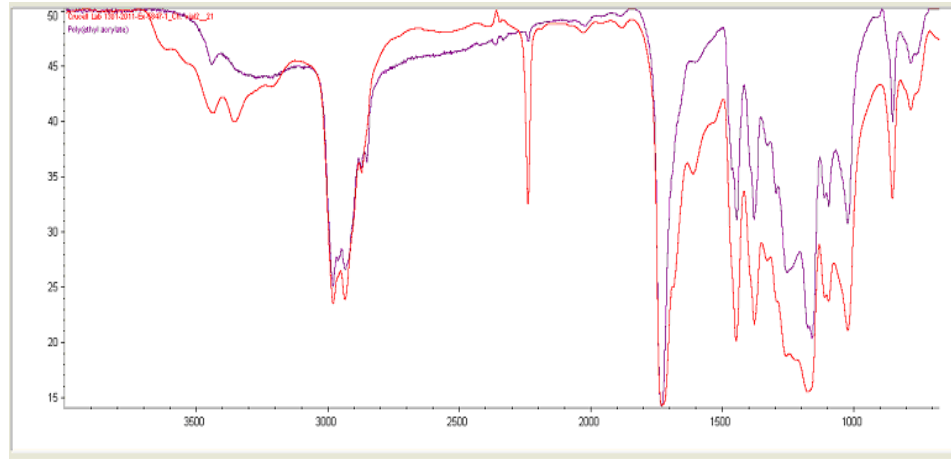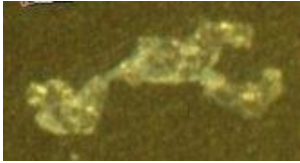


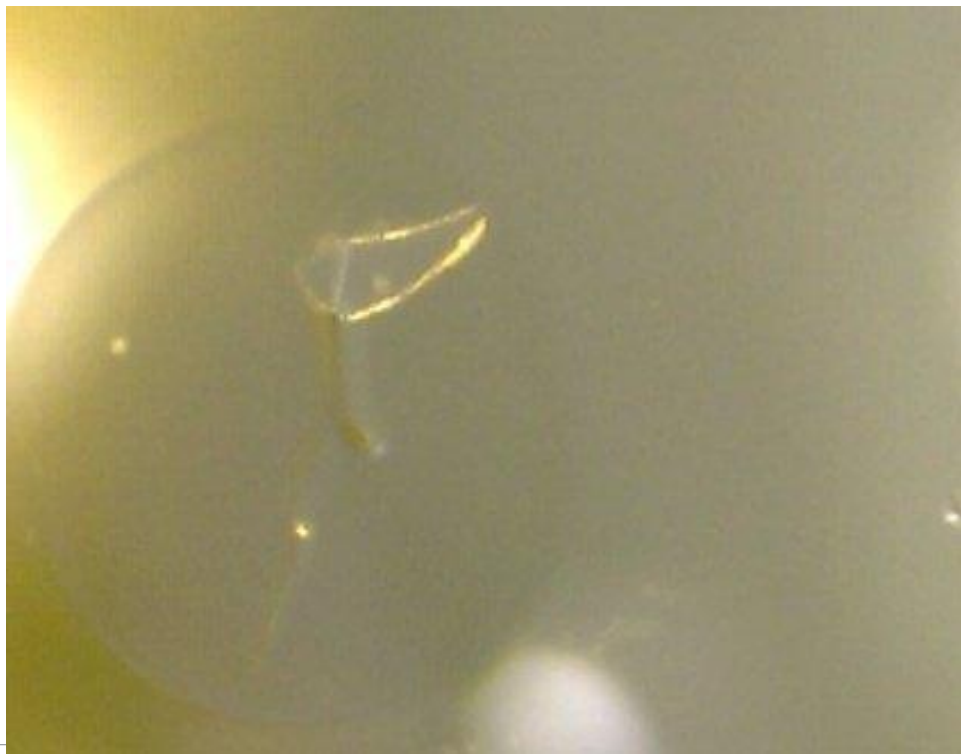

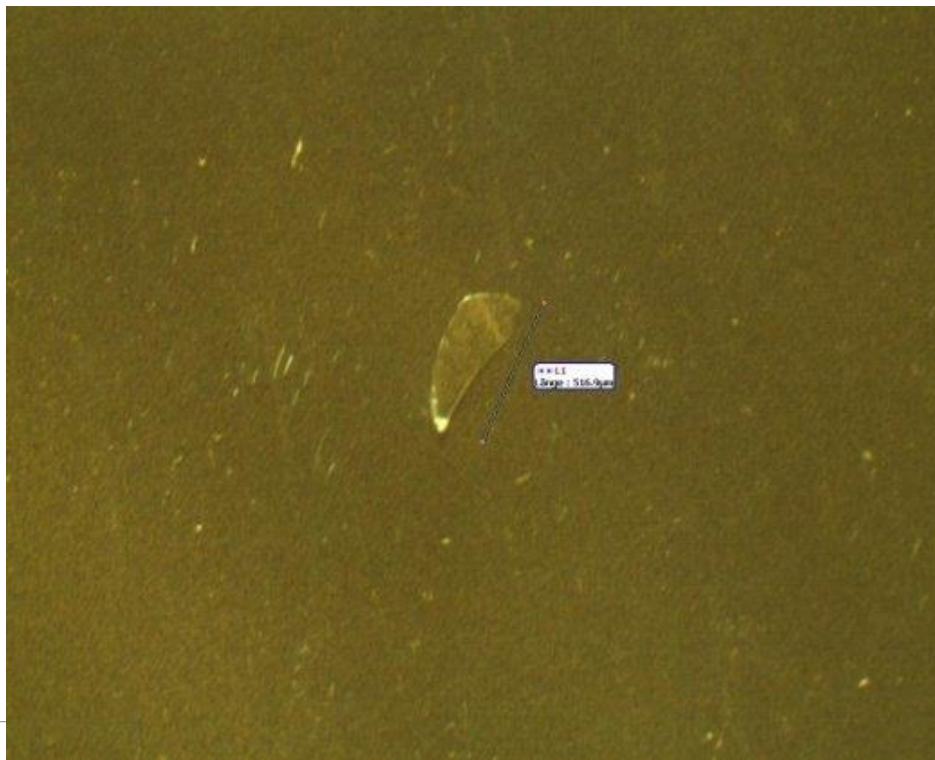


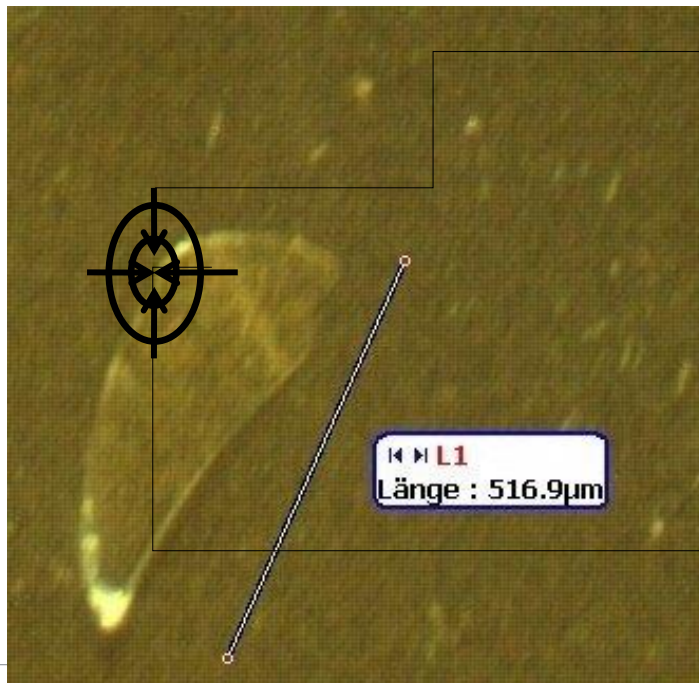

LIBS

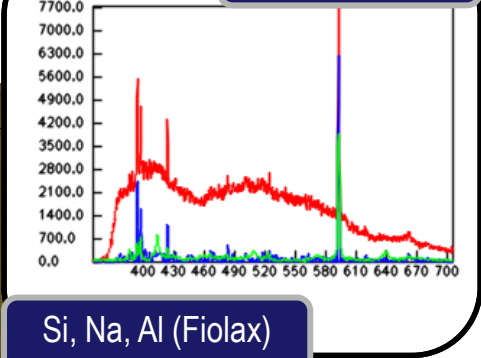

Raman

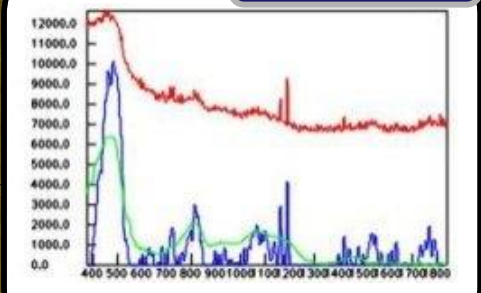

Glass







# CELLULOSE SOURCE






- 4 batches failed in a row
- 3 samples of each of the failed batches and one of the good batches were investigated
- Soon it became clear that the problem was cellulose related....

# Several cellulose fibers were found

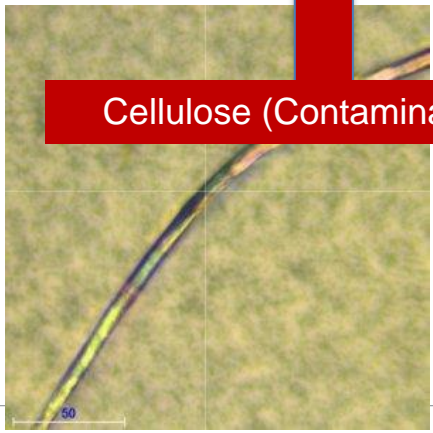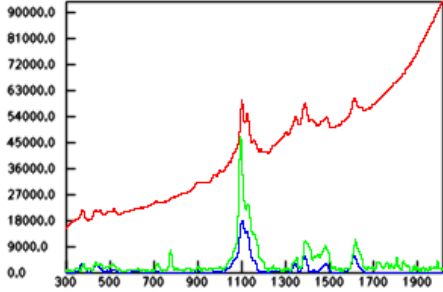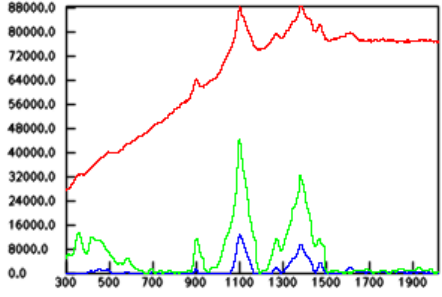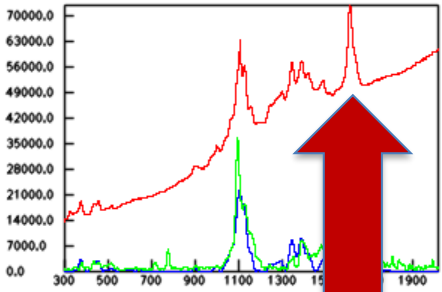

Cellulose (Contaminant)

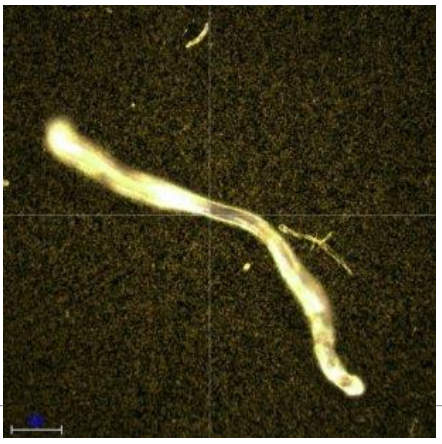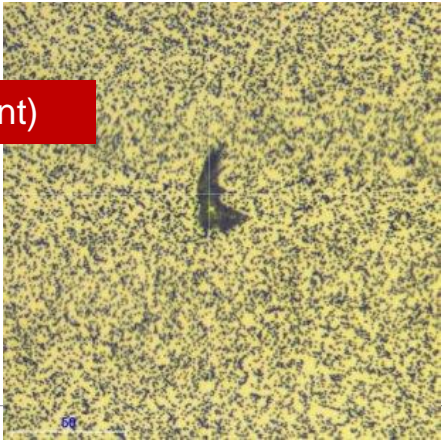


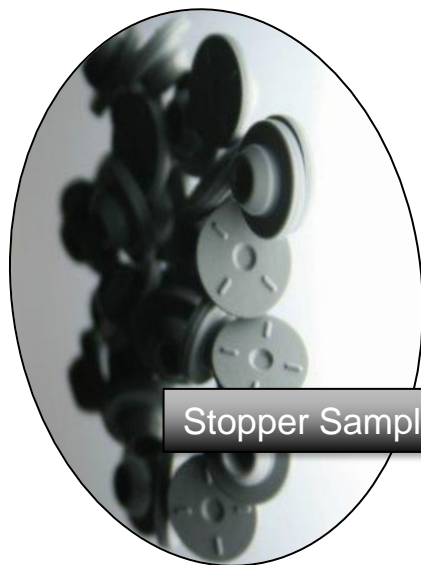

Stopper Sample

Before Tubing Rinse Sample


After Tubing Rinse Sample

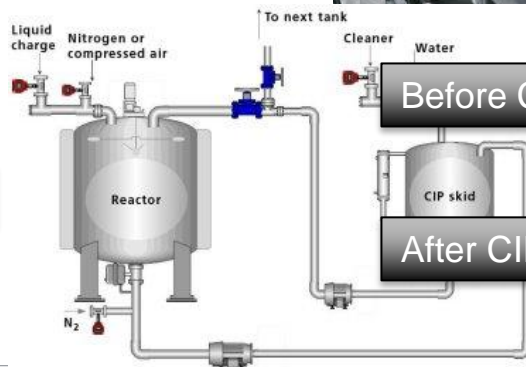



Before CIP Rinse Sample

After CIP Rinse Sample

# Samples from the process were taken<sup>4</sup>

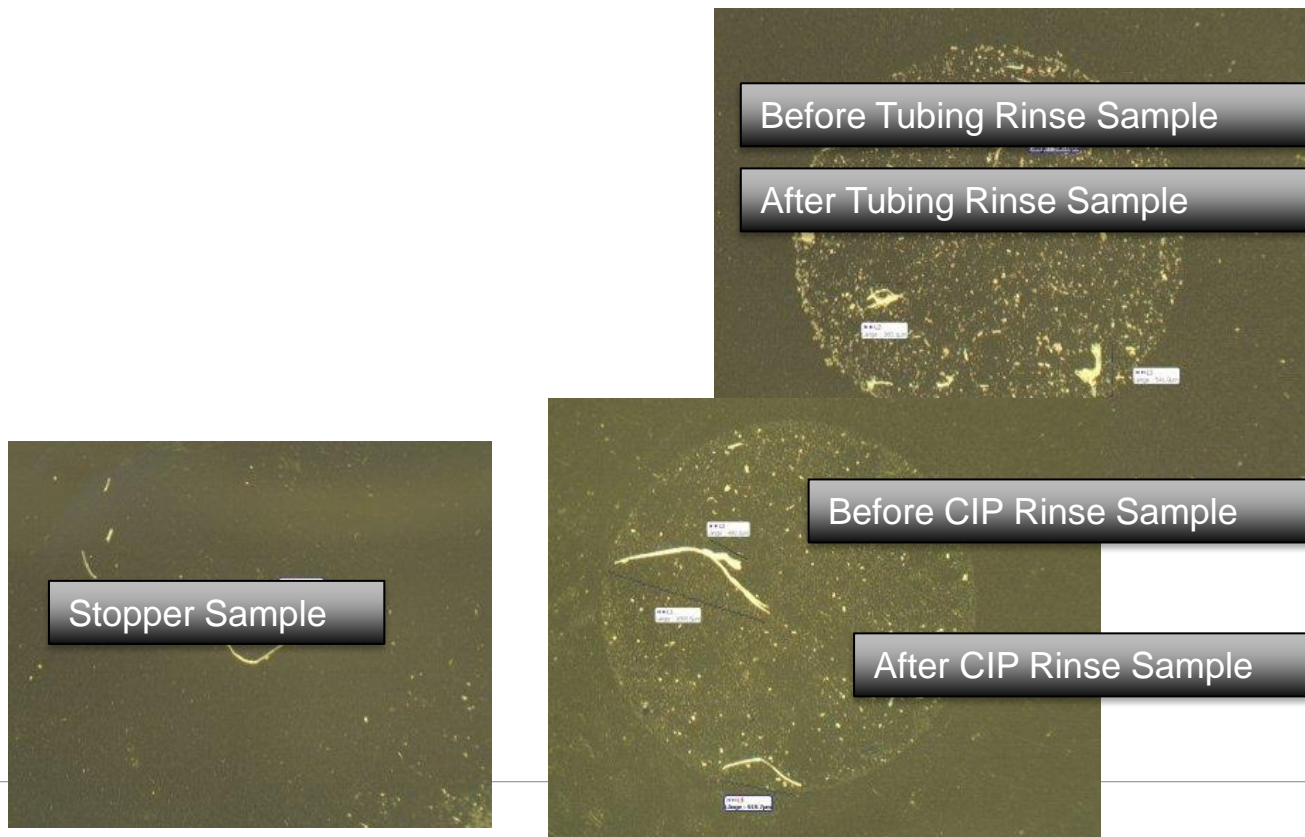


# Database with filling line related materials was built

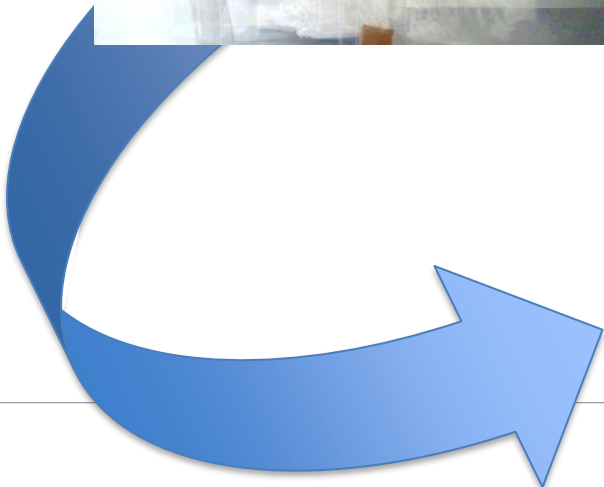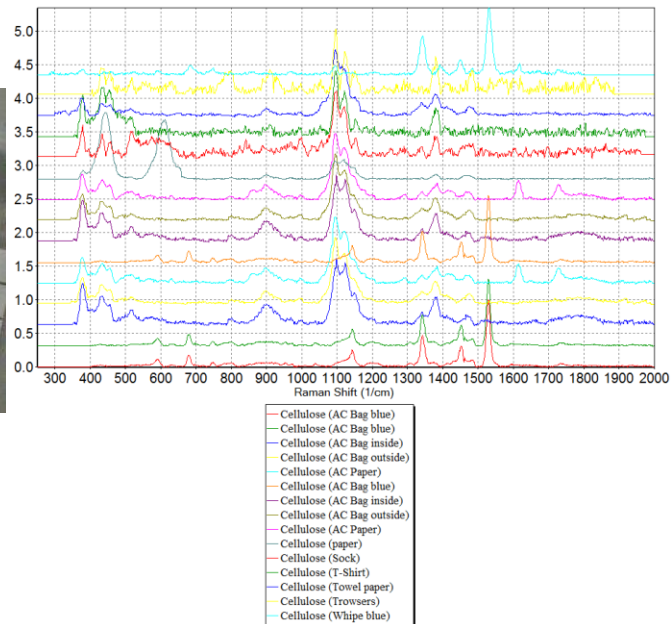

**No Cellulose (Contaminant) !**


# Tube rinse result

Size and Substance Distribution of Measured Particles						
Substance	Number	Size Distribution [ $\mu\text{m}$ ]				
		$\geq 5$	$\geq 10$	$\geq 25$	$\geq 50$	$\geq 100$
-	-	$\geq 5$	$\geq 10$	$\geq 25$	$\geq 50$	$\geq 100$
Cellulose (AC Bag blue)	5	0	0	0	1	4
Cellulose w. Polyester (Papertowel II)	1	0	0	0	1	0
Ethyl Cellulose	1	0	0	0	0	1
Cellulose (AC Bag inside)	19	0	0	0	6	13
Pigment, Indian Yellow	1	0	0	0	0	1
Other Particles	143	0	0	5	38	100
beta-Carotene	50	0	0	3	19	28
Skipped particles	2283	889	808	432	137	17
All particles	2503	889	808	440	202	164

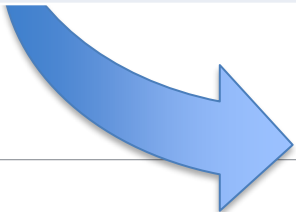

**No Cellulose (Contaminant) !**

# Closer look into the API production (site in Italy)<sup>48</sup>

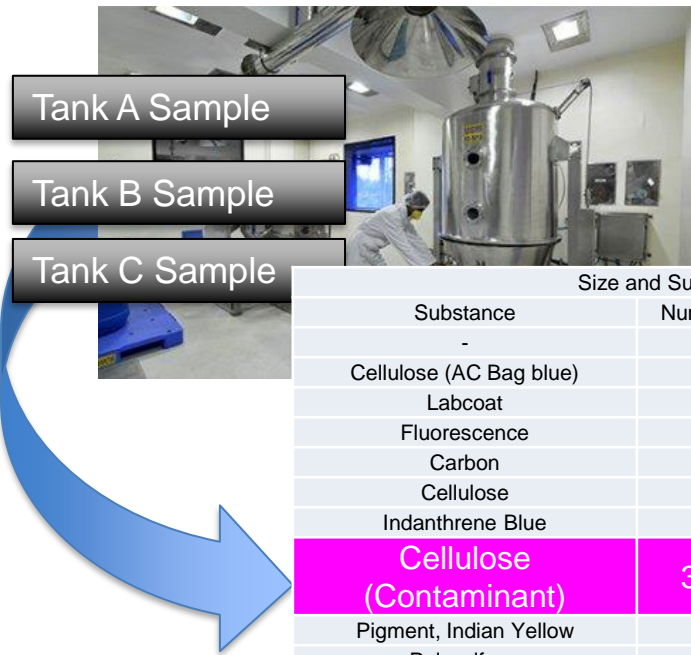

Size and Substance Distribution of Measured Particles						
Substance	Number	Size Distribution [µm]				
		>=5	>=10	>=25	>=50	>=100
-	-	>=5	>=10	>=25	>=50	>=100
Cellulose (AC Bag blue)	1	0	0	0	1	0
Labcoat	1	0	0	1	0	0
Fluorescence	1	0	0	1	0	0
Carbon	4	0	0	3	1	0
Cellulose	1	0	0	0	1	0
Indanthrene Blue	1	0	0	1	0	0
<b>Cellulose (Contaminant)</b>	<b>31</b>	<b>0</b>	<b>0</b>	<b>8</b>	<b>18</b>	<b>5</b>
Pigment, Indian Yellow	3	0	0	3	0	0
Polysulfone	5	0	0	1	2	2
Cellulose (Towel paper)	5	0	0	5	0	0
Other Particles	28	0	0	22	1	5
Skipped particles	1716	1353	362	1	0	0
All particles	1797	1353	362	46	24	12



# Samples from API tanks and tubings showed this type of fiber.

Tank A Sample

Tank B Sample


Tank C Sample



Size and Substance Distribution of Measured Particles

Substance	Number	Size Distribution [µm]				
		>=5	>=10	>=25	>=50	>=100
-	-	>=5	>=10	>=25	>=50	>=100
Cellulose (AC Bag blue)	1	0	0	0	1	0
Labcoat	1	0	0	1	0	0
Fluorescence	1	0	0	1	0	0
Carbon	4	0	0	3	1	0
Cellulose	1	0	0	0	1	0
Indanthrene Blue	1	0	0	1	0	0
<b>Cellulose (Contaminant)</b>	<b>31</b>	<b>0</b>	<b>0</b>	<b>8</b>	<b>18</b>	<b>5</b>
Pigment, Indian Yellow	3	0	0	3	0	0
Polysulfone	5	0	0	1	2	2
Cellulose (Towel paper)	5	0	0	5	0	0
Other Particles	28	0	0	22	1	5
Skipped particles	1716	1353	362	1	0	0
All particles	1797	1353	362	46	24	12

# Update of the library with towels used in API production

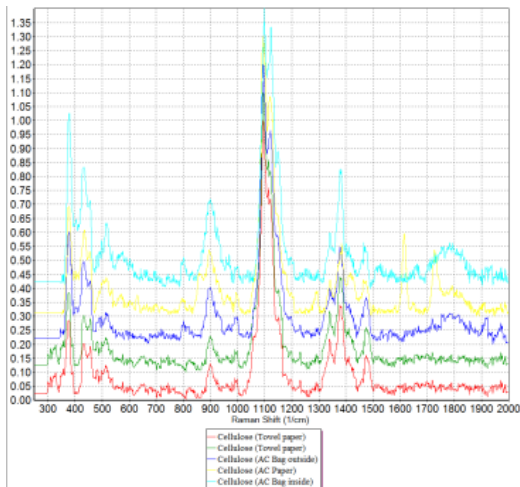



**Cellulose (Contaminant)**

- One special type of cellulose could be identified by the typical peak @ 1600
- Database was built with suspect cellulose samples used in production
- These Cellulose (contamination) fibers were found in smaller concentration in CIP rinses  
no fibers ...were found in the process prior to filling!
- Samples from API tanks and tubings showed this type of fiber.

→ API manufacturer used  
paper towels and introduced  
cellulose into the process

# Control Your Packaging Material

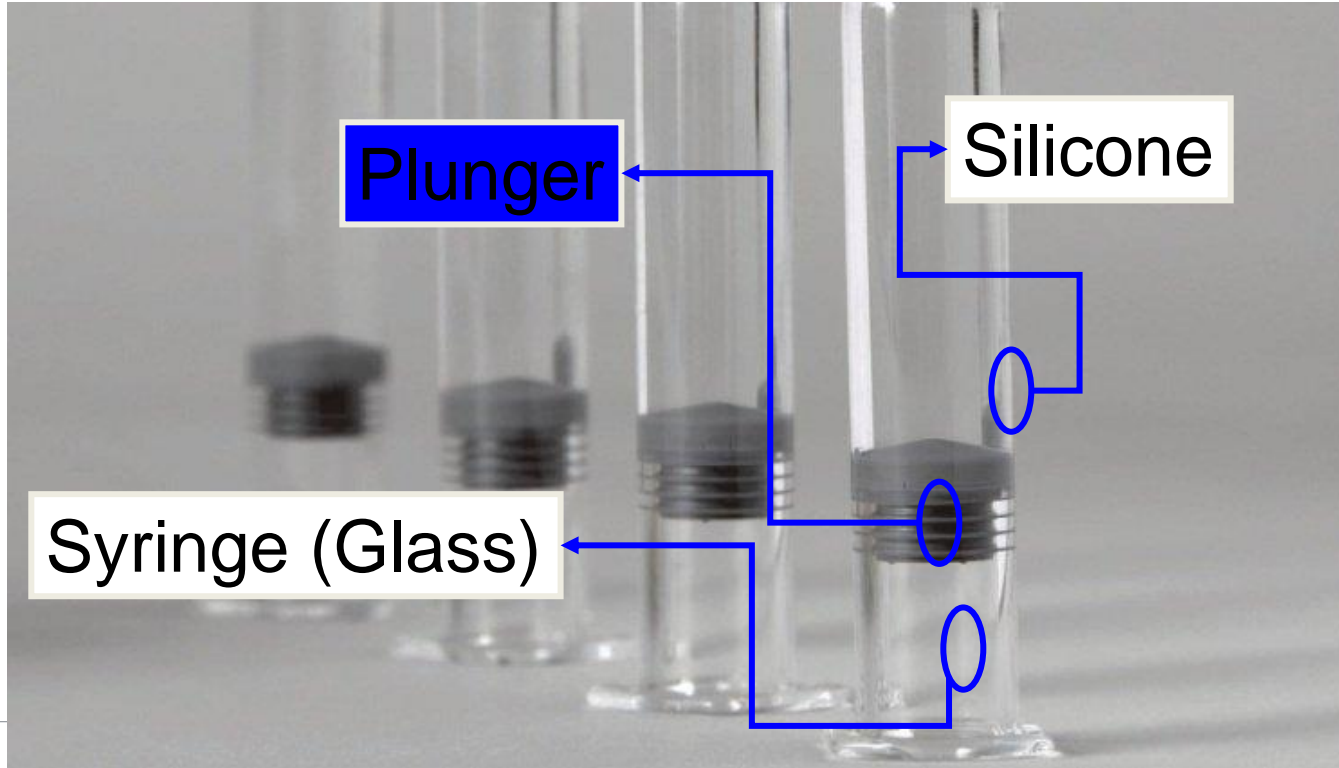

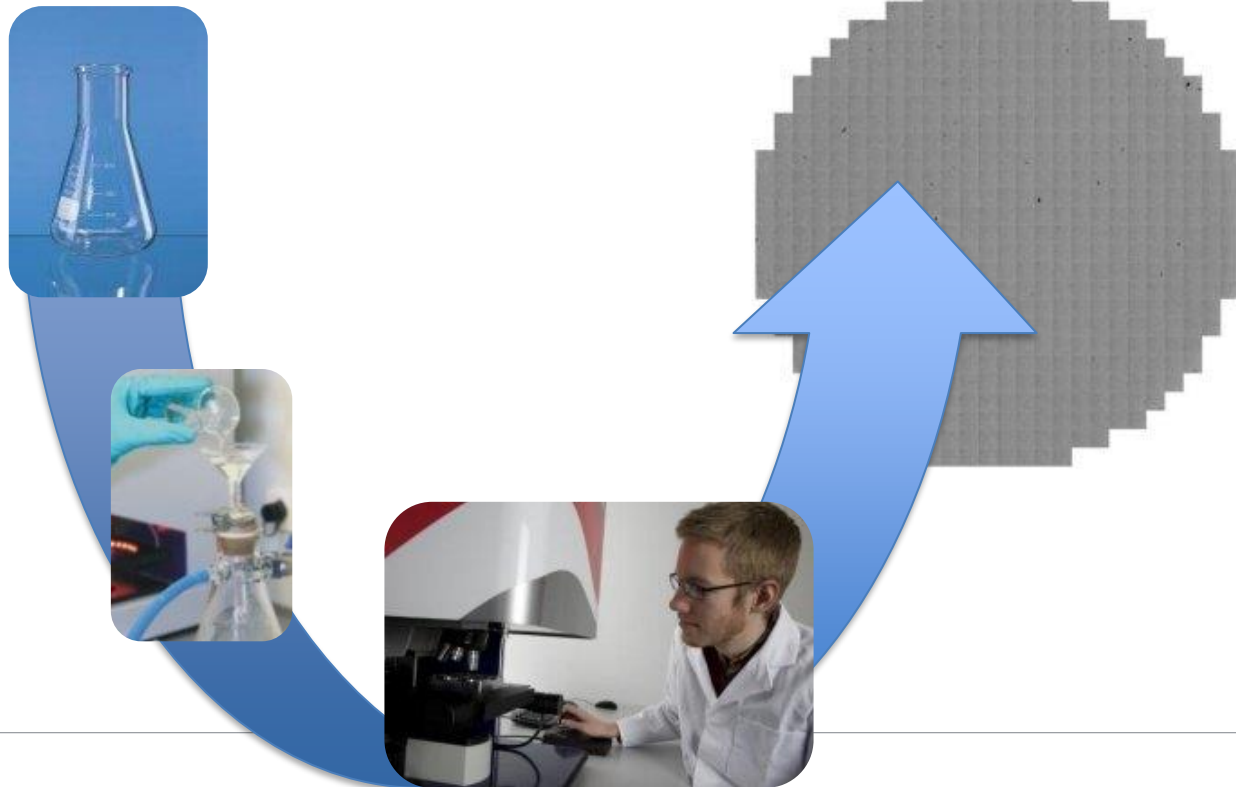


## Technical Report No. 85

### Enhanced Test Methods for Visible Particle Detection and Enumeration on Elastomeric Closures and Glass Containers

**Table 4.1.1-1** Threshold Value to Use when Classifying Particles as Visible or Subvisible (by methods more sensitive as compared to the unaided eye)

Category	Aspect Ratio (length:width)	Visible Threshold	Subvisible
Particle	<5	100 µm	< 100 µm
Fiber	≥5	300 µm	< 300 µm


A thorough discussion of the sample preparation process and the counting methodology used to evaluate within and between operator replicate samples can also be found in **8.2 Appendix B**.

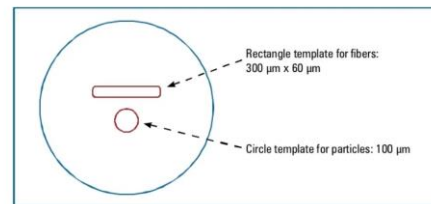

**Figure 4.1.2-1** Microscope Reticle Design For Elastomer Component Particle Analysis


- A number of parts (normalized for surface area) are placed in an Erlenmeyer Flask,
- Add 50 ml of surfactant solution is dispensed and added to the flask.
- Agitate on an orbital shaker for 20 sto remove visible particles from the surface.
- Filter immediately through a membrane filter (a gray filter was used to enhance contrast for both light and dark colored particles and fibers)
- The rinsing process is repeated
- Once the filter is dry, any visible particles present are counted by using a specialized reticle and an optical stereomicroscope
- **Appendix B. Method: Determination of Visible Partides and Fibers on Elastomeric Components by Membrane Filtration and Microscopic Examination**

- 10 stoppers contaminated with fiber  
Cleaning following ISO 8871
- 43 particles > 100  $\mu\text{m}$  found

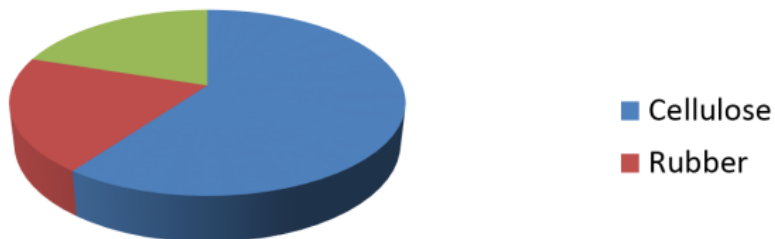

Large scattering in particle number and composition can be observed in one batch and different bags

- 10 stoppers contaminated with particles Cleaning following ISO 8871
- 122 particles found > 100  $\mu\text{m}$

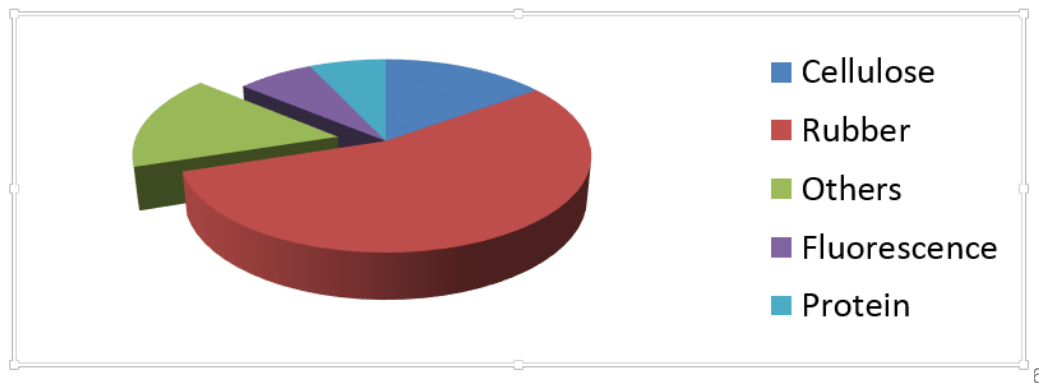


6





Stopper Bags have an impact  
or reflect stopper quality

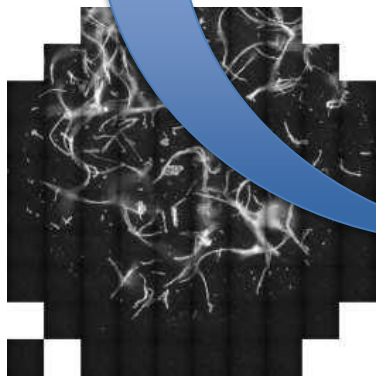


Fibres collected from one bag;  
375 particles > 25  $\mu\text{m}$




Fibres collected from one bag;  
45 particles > 25  $\mu\text{m}$


Test Procedure:  
Bag rinsed with  
250 ml water /  
SDS, filtration,  
counting

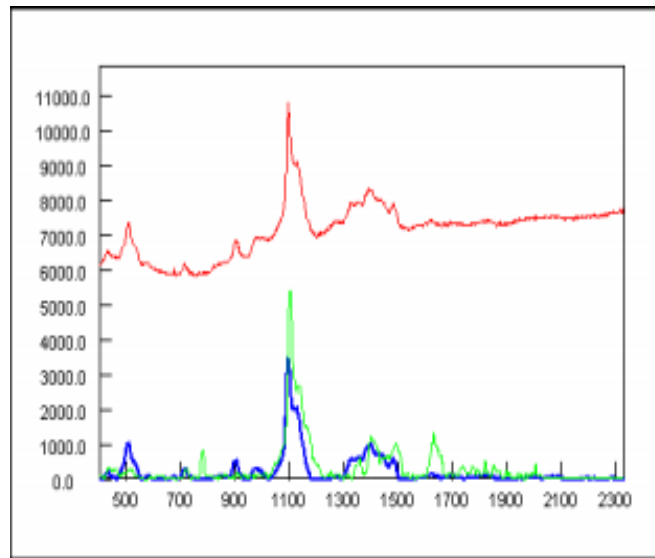


RESULT: Cellulose [Paper]  
RANK: 882, S/N: 39.2

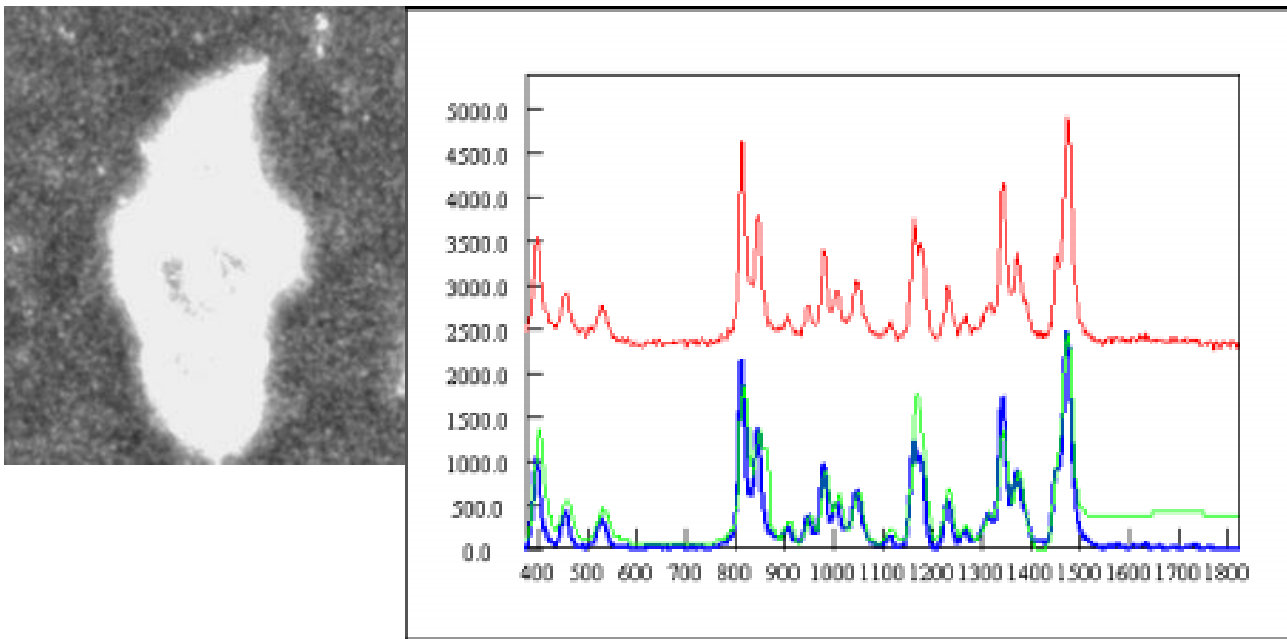



Rubber material and filler

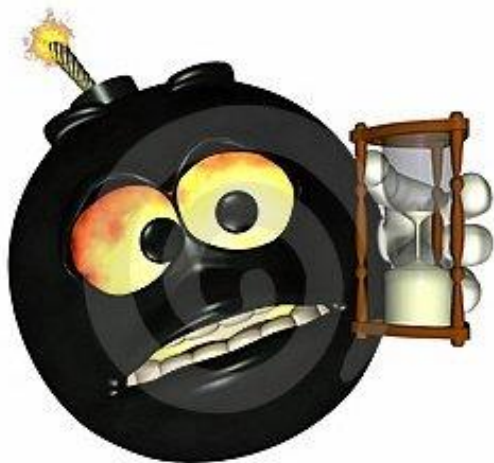


- Increase of rejects with time
- Chemical reactions taking some time
  - Silicone oil on stoppers:  
Agglomeration of Proteins
  - Coatings
  - Glass delamination

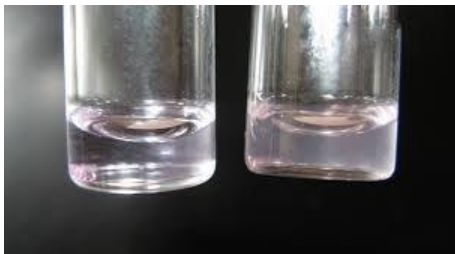


Observation of haziness and aggregates in a new a new batch after slight process change

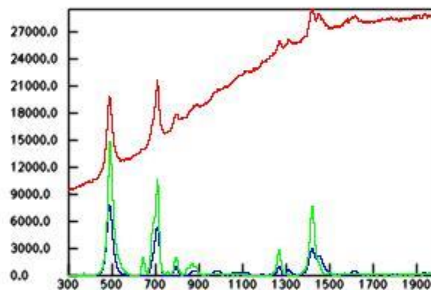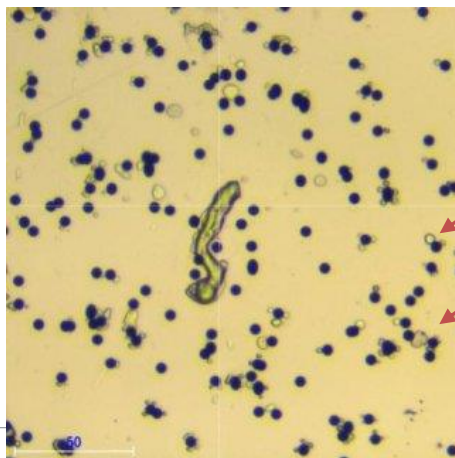

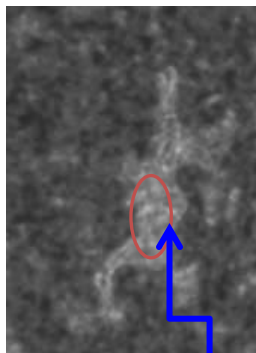


Protein



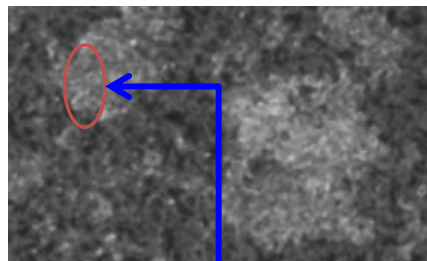




Silicone

Protein

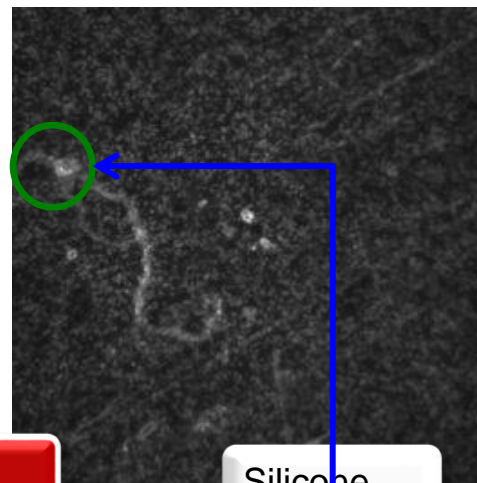


Silicone

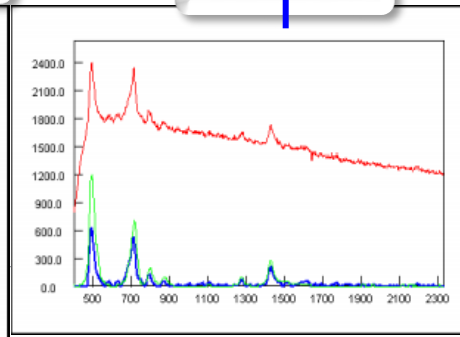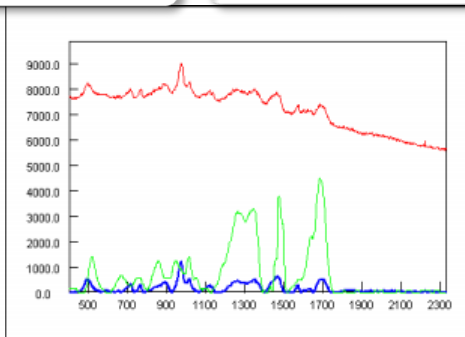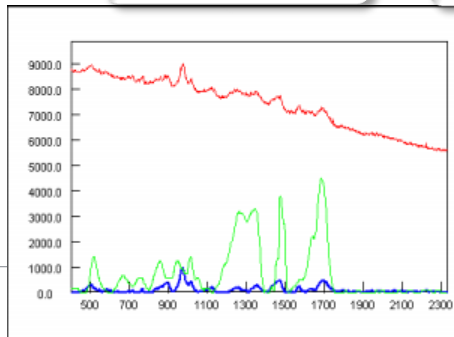

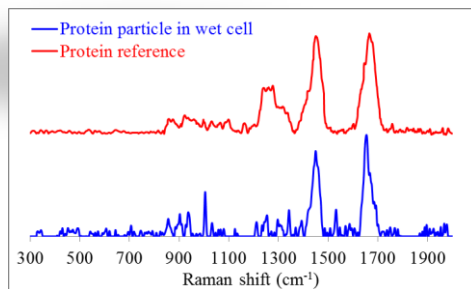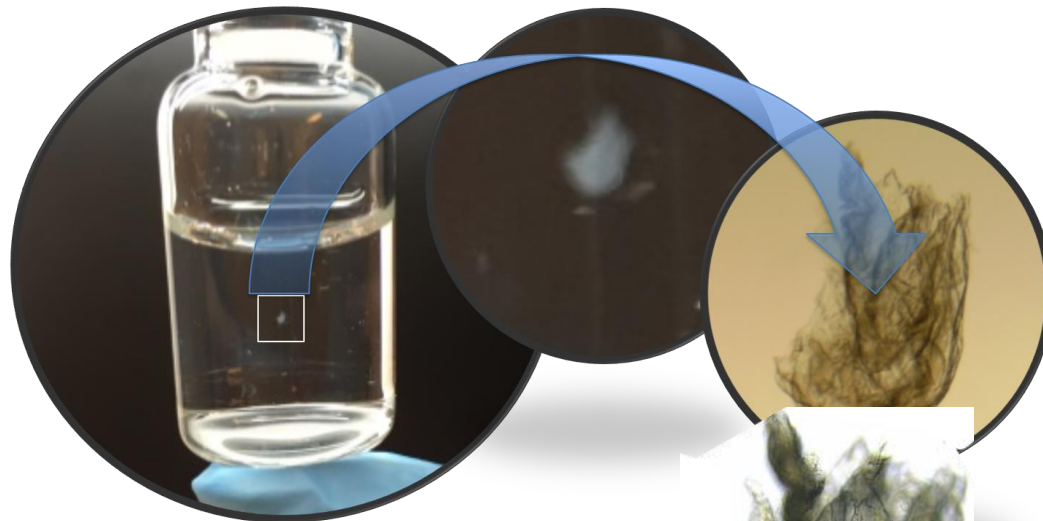

Increasing number of rejects in visual inspection with time

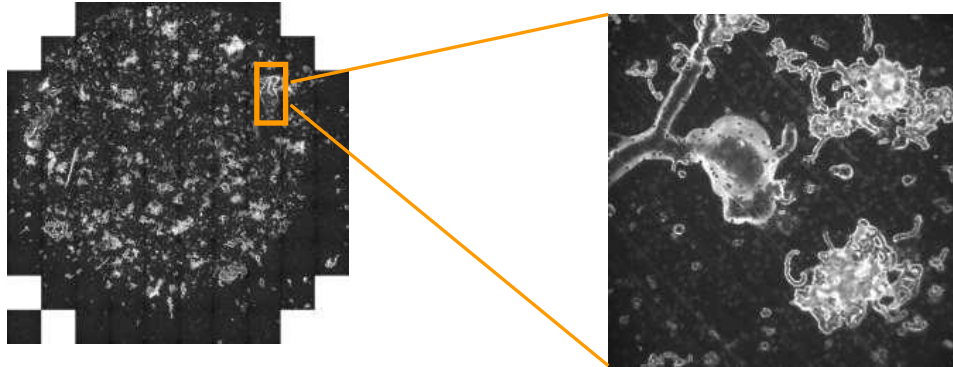

Size and Substance Distribution of Measured Particles					
Substance	Number	Size Distribution [µm]			
-	-	>=10	>=25	>=50	>=100
Proteine	6	0	0	1	5
Fluorescence	18	0	0	1	17
Coating	185	23	44	32	86
<b>Skipped particles</b>	3058	2142	657	232	27
<b>All particles</b>	3267	<b>2165</b>	<b>701</b>	<b>266</b>	<b>135</b>



Destructive reconstitution, dilution, transfer, clearing, solubilizing, filtration, screening, or sieving that allows a product to be visually examined or evaluated microscopically to determine the presence, type, and size of foreign particulate contamination present within the product, container, or device.

## Destructive Inspection and Test Methods

- Reconstitution
- Filtration
- Clarification
- Transfer Dilution
- Sieve/Mesh
- Panning
- Rinse/Flush and Filtration



### Technical Report No. 79

Particulate Matter Control in Difficult to Inspect Parenterals



## 5.3 DIP Product Formulations

Common inspection or testing approaches for DIP product formulations are listed in **Table 5.3-1**.

**Table 5.3-1** Common Inspection or Testing Approaches for DIP Product Formulations

DIP Formulation Type	Common Destructive Methods Applied	Method #
<b>Deeply colored solutions</b> (opaque)	Filtration and microscopic exam in sub-visible and/or visible ranges	2
	Transfer and dilution (if required) in a verified clean transparent container followed by visual inspection	4
<b>Emulsions</b>	Clarification and visual inspection	3
	Clarification → Filtration and microscopic exam in sub-visible and/or visible ranges	3
	Sieving	5
	Additional considerations: – Inspection of settled product with observation of bottom layer for dispersion of dense (sinking) metallic or glass particles	
<b>Gels</b>	Direct visual inspection (USP <790> with modifications, if needed, for increased illumination and dwell time)	USP790
	Dilution → Filtration and microscopic exam in sub-visible and/or visible ranges	4
<b>Lyophilized</b> (freeze-dried product)	Reconstitution and visual inspection	1
	Reconstitution → Filtration and microscopic exam in sub-visible and/or visible ranges	2
	<1 ml Small volumes reconstitution and pooling	4
<b>Powders, API</b>	Reconstitution and visual inspection	1